

*Historical Insight*

# The Discovery and Acceptance of the Kirkendall Effect: The Result of a Short Research Career

[Hideo Nakajima](#)

**Editor's Note:** Some of the artwork employed here was photographically reproduced from existing publications. As a result, the quality of the images is sometimes less than ideal.

*In the 1940s, it was a common belief that atomic diffusion took place via a direct exchange or ring mechanism that indicated the equality of diffusion of binary elements in metals and alloys. However, Ernest Kirkendall first observed inequality in the diffusion of copper and zinc in interdiffusion between brass and copper. This article reports how Kirkendall discovered the effect, now known as the Kirkendall Effect, in his short research career.*

## CONTENTS

- [INTRODUCTION](#)
- [KIRKENDALL'S CAREER](#)
- [THE FIRST PAPER \(1939\) AND D.Sc. DISSERTATION](#)
- [THE SECOND PAPER \(1942\)](#)
- [THE THIRD PAPER \(1947\)](#)
- [MEHL'S CRITICISM AND EXPERIMENTS](#)
- [WHY KIRKENDALL STOPPED HIS RESEARCH CAREER](#)
- [CONCLUSION](#)
- [ACKNOWLEDGEMENTS](#)
- [References](#)

## INTRODUCTION


The fragrance of flowers in a corner of a room drifts even to far distances. When one droplet of ink is dripped into a cup of water, the ink soon spreads, even without stirring, and quickly becomes invisible. These facts show that even if there is no macroscopic flow in a gas or a liquid, molecular movement (i.e., diffusion) can take place, and different entities can mix with each other.

Is atomic diffusion possible in a solid metal where atoms arrange themselves regularly? The answer is yes. Although atomic diffusion in solids is far slower than that in gases and liquids, diffusion does take place. The diffusion in solids is clearly related to various processes such as recrystallization, precipitation, and oxidation. Such study of the diffusion in solids was initiated just 100 years ago when Sir Roberts-Austen<sup>1</sup> discovered the diffusion phenomenon of gold in solid lead in 1896. For a long time afterward, people believed that atomic diffusion occurred by a direct exchange mechanism or a ring mechanism in metallic crystals (Figure 1).

In 1947, Ernest Kirkendall reported the results of experiments on the interdiffusion between copper and zinc in brass and observed



the movement of the interface between the different phases due to high-temperature interdiffusion, now called the Kirkendall Effect. This phenomenon supported the idea that atomic diffusion occurs through vacancy exchange. Since its discovery, the Kirkendall Effect has been found in various alloy systems, and studies on lattice defects and diffusion developed

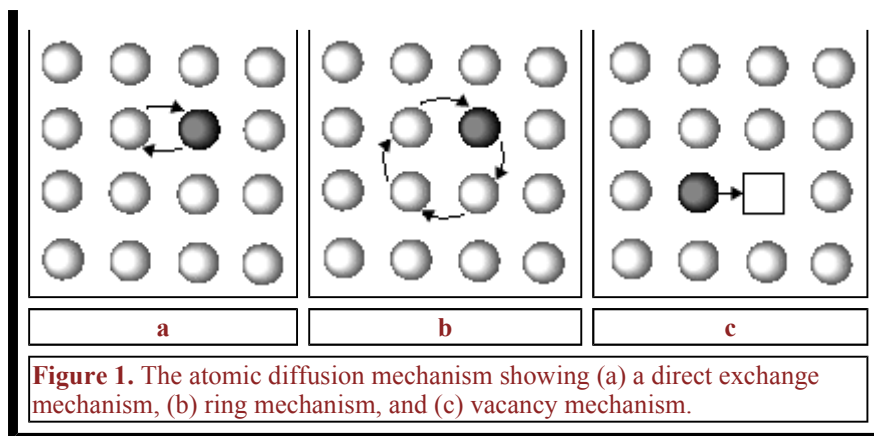

significantly. The Kirkendall Effect is important in connection with bonding between different materials and, in particular, raises the practical concern of controlling and suppressing the voids that are produced in the boundary region at a bonding interface. Today, the effect has been taken into account in various fields in materials science and technology such as structural materials welding, metals and ceramics powders sintering, thin films, and large-scale integration.

When the International Conference on Diffusion in Metals and Alloys was held in 1988 in Balatonfured, Hungary, S. Rothman of [Argonne National Laboratory](#) (and also the editor of *Journal of Applied Physics*) told me of an episode during the discovery of the new effect by Kirkendall. Kirkendall's idea had been criticized by many researchers, but he kept trying until his interpretation had almost been accepted. When a search committee was set up to determine Kirkendall's possible promotion to associate professorship, one of the referees, R.F. Mehl of the [Carnegie Institute of Technology](#) (an authority on diffusion), rejected Kirkendall's promotion. Shortly thereafter, Kirkendall gave up his academic career and took a job as secretary of the [American Institute of Mining and Metallurgical Engineers](#) (AIME). Although the story related by Rothman was certainly interesting to me, my boss at that time (H.B. Huntington, [Rensselaer Polytechnic Institute](#)) told a different version of the story, and I wondered which version was right.

Fifty years have passed since Dr. Kirkendall finished his academic career. Fortunately, several friends informed me that he was still in good health, and I succeeded in calling him when I was staying in Canada in 1993. I was so excited to talk with him; he politely replied to my various inquiries and kindly suggested I visit him at his home "since such a telephone conversation is not sufficient." At that time, I could not visit him because I had to leave Canada to return to Japan within a few days. Two months later, I finally visited his home and interviewed him. Based on that meeting, this article reports how Kirkendall discovered the Kirkendall Effect in a short research career in which he produced only three papers.<sup>2,4</sup>

## KIRKENDALL'S CAREER


Ernest Kirkendall was born in Michigan in 1914. He graduated from Wayne College (later [Wayne University](#)) in 1934, was awarded a master's degree in 1935 and a doctor of science in 1938 from the Metallurgy Department at the [University of Michigan](#). He was an instructor at [Wayne University](#) from 1937 to 1941 and an assistant professor from 1941 to 1946, during which time he wrote the famous paper "Zinc Diffusion in Alpha Brass" with Smigelskas.<sup>4</sup> From 1947 to 1965, he served as secretary of [AIME](#); he then became a manager at the United Engineering Trustees. He concluded his career as a vice president of the [American Iron and Steel Institute](#) from 1966 and 1979.

To illustrate the importance of his discovery, the Kirkendall Effect Symposium on Interdiffusion and Phenomena that Depend on Net Vacancy Flows was held during the [TMS](#) Fall Meeting in October 1991. I heard that this was successful meeting, attended by authors such as professors Turnbull,

Balluffi, Huntington, Cahn, and Heumann, who had contributed to lattice defects and diffusion research in the period following the discovery of the Kirkendall Effect.

## THE FIRST PAPER (1939) AND D.Sc. DISSERTATION

In 1935, Kirkendall began his research work under the direction of Upthegrove in the Metallurgy Department at [University of Michigan](#). At the beginning, he learned much from the reviews by Desch (1912),<sup>5</sup> Mehl (1936),<sup>6</sup> and Krynit-sky (1937).<sup>7</sup> He developed much interest in atomic diffusion phenomena in solid metals and, in particular, was significantly influenced by Mehl's review. Furthermore, he was much interested in equilibrium-phase diagrams, particularly the phase separation of  $\alpha$ -brass and  $\beta$ -brass resulting from the cooling of  $\beta$ -brass alloy. For his research topic, he selected diffusion in brass, which was a combination of those two interests. Although such research had already been done by several researchers, most were nothing more than qualitative discussions, and none of the research could elucidate the key questions until quantitative evaluation and discussion had been achieved. Thus, Kirkendall wanted to measure the diffusion coefficients of copper and zinc in  $\alpha$ -brass quantitatively with high accuracy by using a "new method." The result was his D.Sc. dissertation,<sup>2</sup> which reported zinc diffusivities in brass at three different temperatures.

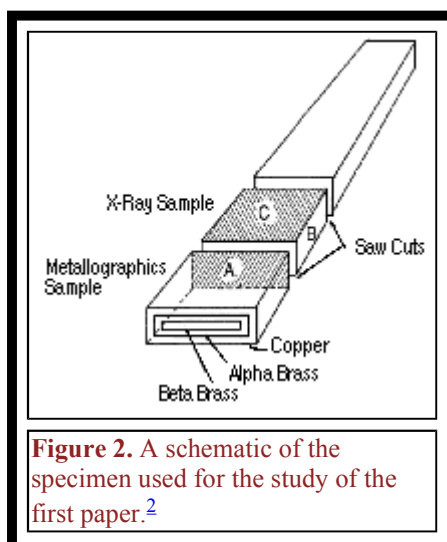


The side face of the  $\beta$ -brass plate-shaped specimen (100 mm in length and about 3 mm in thickness) was first mirror-polished; it was then electroplated with 250  $\mu$ m thickness of copper (Figure 2). The specimens were annealed in vacuum at 723 K for about 10 ks to make hydrogen desorb from the specimens. Diffusion anneals were carried out in a muffle electric furnace at a specific temperature and for a specific duration. After water quenching, a part of the specimen was cut off, while the remainder was used for successive diffusion anneals. The metallographic observation of the polished surface A was performed with an optical microscope. X-ray diffraction was taken from the polished surface B after each sectioning step of 25-75  $\mu$ m thickness to measure the lattice parameters, which were then converted to determine the zinc concentration in  $\alpha$ -brass (Figure 2).

After diffusion anneals, an  $\alpha$ -brass phase layer grows on both sides of the bonding interface of copper and  $\beta$ -brass (Figure 3). The  $\alpha$ -brass layer inside the interface consists of large columnar grains so that the  $\alpha/\beta$  phase boundary is clear. On the other hand, since the copper-rich  $\alpha$ -brass phase outside the interface has the same crystal structure as the copper phase, the boundary is not distinct.


Kirkendall told me, "The quantitative analysis of the work was possible owing to two points—the  $\alpha$ -brass phase in between the original (bonding) interface and the final  $\alpha/\beta$  interface always grows uniformly in thickness, and the  $\alpha/\beta$  interface can be observed clearly with the optical microscope. If the  $\alpha/\beta$  interface and the columnar grains formed on the inside of the original copper  $\beta$ -brass interface had not been distinct, the Kirkendall Effect would not have been discovered. Thus, I was lucky to choose the system of copper and brass originally." He measured the concentration profiles of copper diffusion in  $\alpha$ -brass phase surrounded by both the original and the  $\alpha/\beta$  interfaces.

Although his first paper<sup>2</sup> did not mention it, he told me, "I had noticed that the location of the original interface after diffusion anneal was different from the Boltzmann-Matano interface

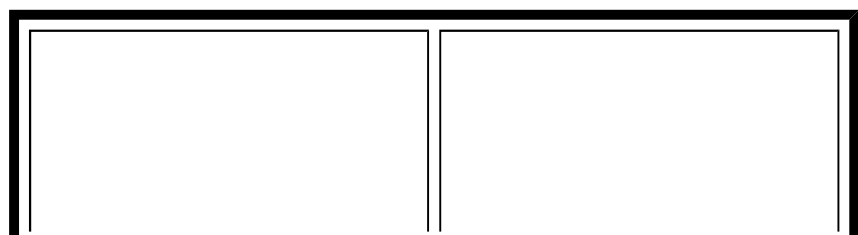


when I was a graduate student. And I did not necessarily think about the possibility of inequality of the diffusivities of copper and zinc ( $D_{Cu} \neq D_{Zn}$ )." The Boltzmann-Matano interface fixes two equal areas on the concentration profile  $c(x)$ ; it is the plane through which equal amounts of material have moved in positive and negative directions.

At that time, it was common belief that atomic diffusion took place via a direct exchange or ring mechanism. None of the researchers proposed other mechanisms. Thus, according to his advisor's suggestion, "I preferred to explain the movement of the original interface as due to volume change between  $\alpha$ - and  $\beta$ -brass;  $\alpha$ -brass has fcc close-packed structure while  $\beta$ -brass has bcc less close-packed structure." Moreover, he concluded that on the assumption of the equality of the diffusivities of copper and zinc, diffusion of these elements must have occurred by the ring mechanism in which four or more atoms participate. He recalled that if he had insisted on the inequality of these diffusivities to interpret the original boundary migration, Uptegrove would have opposed Kirkendall's Sc.D. thesis defense.

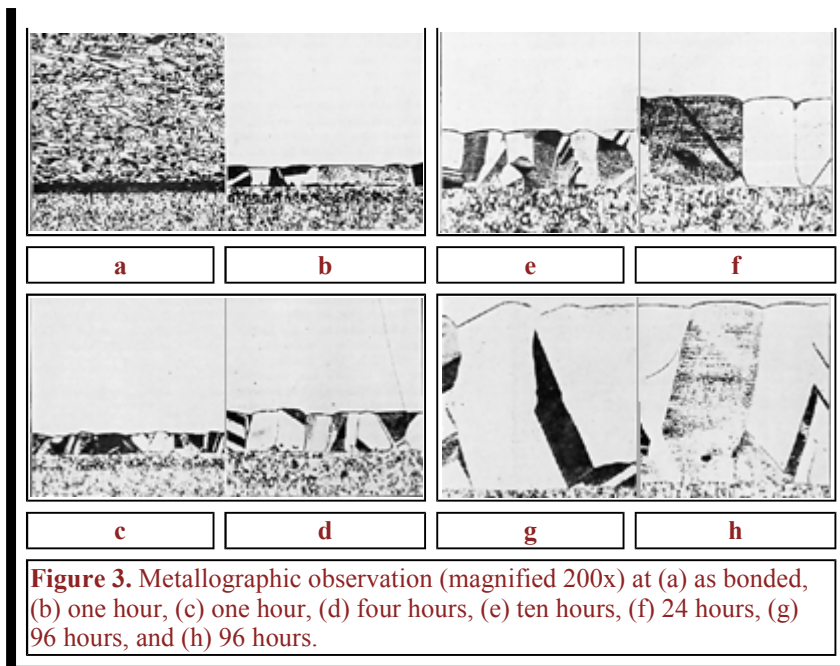

## THE SECOND PAPER (1942)

After Kirkendall had completed his Sc.D. program, he was appointed an instructor at [Wayne University](#). After he returned to his old school, he wrote his second paper.<sup>3</sup> In the abstract he asserted, "That this cyclic interchange in lattice position of solute and solvent atoms in equal numbers is the only true mechanism of diffusion is denied by the evidence presented in this paper." The first paper and the dissertation did not reflect his own thought significantly. However, by this time he was no longer influenced by his advisor; he wrote the second paper as a single author after he had confirmed the validity of his experiments by repeating the measurements.

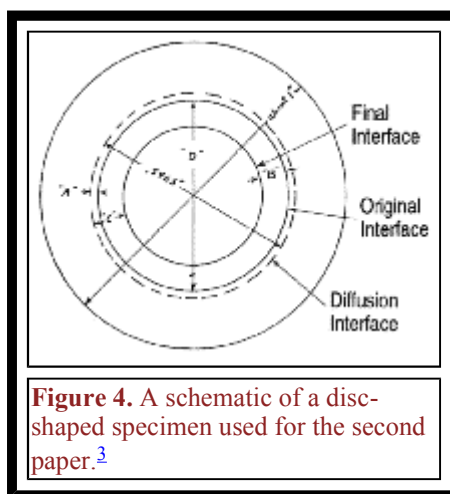

When he moved from the [University of Michigan](#) to [Wayne University](#), Wayne had only just been promoted to university status, and there was very limited equipment in the laboratory. At the time, a friend who had been an alumnus of the [University of Michigan](#) and was now on the staff of [Ford Motor Company](#) was working on the manufacture of x-ray tubes. He gave Kirkendall the blueprints, manuals, and various small parts of an x-ray tube, and Kirkendall made an x-ray tube by himself. As the  $CoK\alpha$ -ray was the most effective for brass samples, an x-ray tube with a cobalt target was produced. Furthermore, he obtained a high-voltage power supply for Röntgen photography from a local dentist, and set up the x-ray diffraction apparatus.

Disc-shaped specimens of 15 mm in diameter were used (Figure 4). Muntz metal with 60.6% copper, 0.1% total impurities, and the balance in zinc was used for the specimen, whose surface was electroplated with copper 5.12 mm in thickness. After the diffusion



anneals, metallographic observation of a section of the specimen was done with the optical microscope, and the displacement between the original interface and the  $\alpha/\beta$  phase boundary was measured. After each removal of a 200-250  $\mu\text{m}$  thick layer by a lathe, x-rays were directed onto the specimen to measure the surface lattice parameter, which yielded zinc concentration profiles in the specimen.

Figure 5 shows metallographic observations after successive diffusion anneal at 1,053 K up to 2,523.6 ks. As seen in the figure, a layer with  $\alpha$ -brass phase was formed on both sides of the original interface. In particular, the  $\alpha$ -brass phase on the  $\beta$ -brass side consisted of large columnar grains, and the  $\alpha/\beta$  interface was very clear because of the different crystal structures in  $\alpha$ -brass (fcc) and  $\beta$ -brass (bcc). On the other hand, in the copper-rich  $\alpha$ -brass phase, neither a distinct difference in the grain size nor a clear  $\alpha$ -brass/copper interface boundary was observed because the crystal structure was the same. Figure 6 depicts the zinc concentration profiles after the different anneals at 1,053 K.

According to [Fick's first law](#), diffusion mass flux ( $dm$ ) across the section A in the direction of a concentration gradient ( $dc/dx$ ) for the time interval ( $dt$ ) can be expressed as

$$dm = -DA (dc/dx) dt$$


where D is diffusivity. Thus, one obtains

$$D = m / (\text{average } dc/dx) \Delta t$$


Applying the above equation to the result shown in Figure 6, the average of the diffusivity at 26% Zinc concentration at 1,053 K was

$$D \approx 3.8 \times 10^{-13} \text{ m}^2\text{s}^{-1}$$

This paper concluded that, at most, one-fifth of the movement of the original interface was due to volume shrinkage accompanied by the phase change from  $\beta$ - to  $\alpha$ -brass, while the remaining four-fifths was attributed to the zinc diffusion being faster than that of copper. This explanation was in contrast to that in the first paper<sup>2</sup> and in the dissertation.

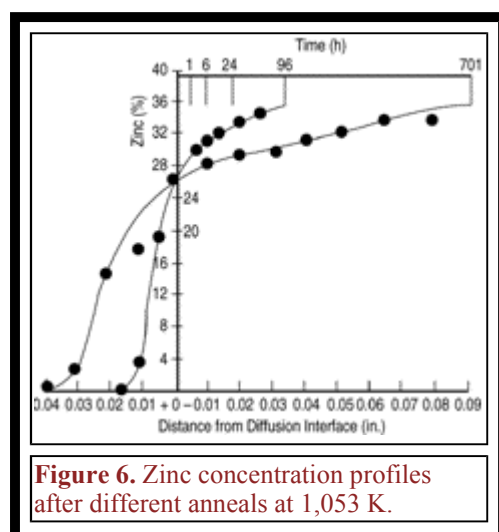

**Figure 6.** Zinc concentration profiles after different anneals at 1,053 K.

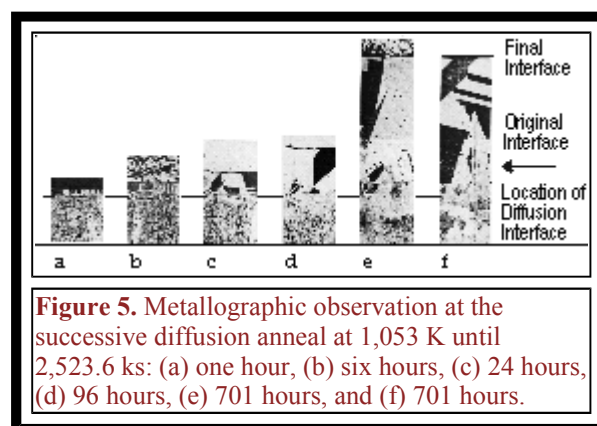

**Figure 5.** Metallographic observation at the successive diffusion anneal at 1,053 K until 2,523.6 ks: (a) one hour, (b) six hours, (c) 24 hours, (d) 96 hours, (e) 701 hours, and (f) 701 hours.

The paper<sup>1</sup> was published in 1942. In the same year, Huntington and Seitz<sup>8</sup> evaluated the activation energy for self-diffusion in copper using electron theory and suggested that self-diffusion occurs by a vacancy mechanism. However, most researchers in the field did not fully recognize the significance of the paper. [World War II](#) began, and neither paper received enough attention. I asked Kirkendall whether he had known the existence of the Huntington-Seitz paper. He had not; even after he wrote the third paper, he did not notice it.


## THE THIRD PAPER (1947)

Alice Smigelskas, a student, joined the Kirkendall research a few years after the second paper was published. In Kirkendall's laboratory, there was only one handmade electric furnace that often had to be used for diffusion annealing for as long as two months. Smigelskas often had to adjust the furnace temperature, sitting down beside the furnace, because the furnace controller at that time was not performing well. Kirkendall, reminiscing, said "In

the early morning of Christmas Day she called to tell me that she could not control the furnace so as to lower the temperature. I was urged to come to my laboratory in a hurry, even though there was a heavy snowfall, leaving my wife and small children at home."

There were two main features of the third paper. First, 70-30 brass (70% copper and 30% zinc) was adopted in order to avoid the large volume change from  $\beta$ -brass to  $\alpha$ -brass. Second, insoluble thin wires of molybdenum were inserted in the bonding interface between the copper and the brass for clear observation of the movement of the original interface.


A brass bar 180 mm long and about 19 mm wide was surface-ground and polished with abrasive paper. Molybdenum wires 127 mm in diameter were stretched lengthwise along each of the two plane surfaces. The specimen was then electroplated with copper to a depth of 250  $\mu\text{m}$  or more during a period of four days. The bar consisted of an  $\alpha$ -brass core, molybdenum wires, and a heavy layer of electroplated copper. Figure 7 is a sketch of the cross section of the bar. Diffusion was carried out at 1,058 K for various lengths of time. The distance between the two sets of molybdenum wire were measured, which identified parallel diffusion planes or interfaces. X-ray diffraction was also carried out to obtain diffusion penetration profiles.

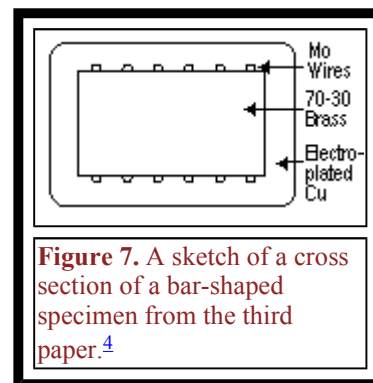

Kirkendall found a shrinkage of the brass core. Figure 8 shows the shift of each interface half the total decrease in interface-to-interface distance. On the basis of the sample analysis described in the second paper, the interdiffusion coefficient was evaluated from these diffusion penetration profiles as

$$D \approx 4 \times 10^{-13} \text{ m}^2 \text{ s}^{-1}$$

This was in good agreement with the previous value  $3.8 \times 10^{-13} \text{ m}^2 \text{ s}^{-1}$ . In this way, he confirmed good reproducibility. Furthermore, he also confirmed from the metallographic observation that zinc diffused into the copper faster than the copper diffused into the brass.

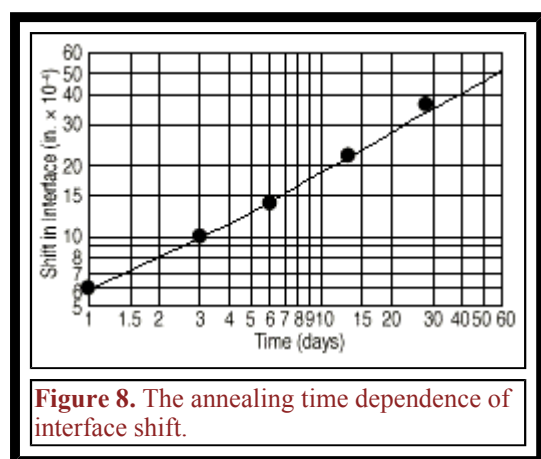

Thus, the significant result was the demonstration that when diffusion takes place in  $\alpha$ -brass, the zinc diffuses much more rapidly than copper. Such diffusion was accompanied by the shrinkage of the high-zinc  $\alpha$ -brass from which zinc diffused out. It was stressed that studies of diffusion and related phenomena consider an unequal interchange of solute and solvent atoms during diffusion and that a mass shift of metal including the interface might result. Finally, he concluded that "diffusion formulas based on an equal interchange of solute and solvent atoms and a substantially stationary interface will be in error."

## MEHL'S CRITICISM AND EXPERIMENTS

When Kirkendall completed his work for the third paper,<sup>4</sup> [World War II](#) had ended. Most researchers' interests shifted from military and applied research toward basic research. In such circumstances, the diffusion problem identified by Kirkendall drew much attention from many people. The paper was submitted to the editorial office of *Transactions of the AIME* in April 1946, where the referee was a leading figure, R.F. Mehl, director of the Metals Research Laboratory,


[Carnegie Institute of Technology](#). He rejected the submitted manuscript for more than six months because he thought it was wrong. Mehl was also a consultant of the Climax Molybdenum Company Research Laboratory; Parke and Ham of the Climax Molybdenum Company, friends of Kirkendall who were unable to look on with indifference any longer, suggested to Mehl that, in fairness, he should criticize and make comments with his opinion in the discussion section of the paper's presentation at a meeting, instead of refusing its publication. At last, Mehl accepted their suggestion, and the Smigelskas-Kirkendall paper<sup>4</sup> was published in 1947. It consisted of five pages of text and, surprisingly, eight pages of comments and discussion. (In those days, comments and discussion were freely published; there was enough space.)

Mehl still doubted the Kirkendall paper. Meanwhile, L.C.C. daSilva from Brazil joined his laboratory as a graduate student. In order to verify that the Kirkendall Effect was wrong, Mehl let the student carry out systematic experiments for interdiffusion, not only in Cu/ $\alpha$ -brass, but also in Cu/Sn  $\alpha$ -solid solution, Cu/Al  $\alpha$ -solid solution, and in Cu/Ni, Cu/Au, and Ag/Au diffusion couples. To the contrary of Mehl's expectation, daSilva found that the marker movement was confirmed and undoubtedly associated with the manner in which atoms move during diffusion (i.e., the Kirkendall Effect was reproducible). Mehl continued to believe, however, that diffusion took place by a direct exchange mechanism so that  $D_A = D_B$ .

A diffusion seminar was held October 21-27, 1950, during the 32nd [ASM](#) National Metal Congress at Chicago, where top-ranking diffusion researchers such as L.S. Darken, C. Wells, J. Bardeen, C. Herring, H.B. Huntington, F. Seitz, R.F. Mehl, D. Turnbull, and J.E. Burke joined together. The details of the seminar were reported in the literature.<sup>9</sup> In this conference most of the attendees approved the validity of the Darken equation, which supported  $D_A \neq D_B$  in interdiffusion, the vacancy mechanism proposed by Huntington and Seitz, and the Kirkendall Effect. During the conference, Seitz thoroughly persuaded Mehl, who, as before, had opposed the vacancy mechanism and the Kirkendall Effect. After a few days, he admitted the validity of the Kirkendall Effect. Mehl himself officially announced in the closing remarks that the Kirkendall Effect was acceptable and that, moreover, his student had much data to confirm the reproducibility of the effect for several alloying systems.<sup>10</sup>

## WHY KIRKENDALL STOPPED HIS RESEARCH CAREER

The search committee for professorships in American universities are in the habit of involving several off-campus members. From 1945 to 1946, Kirkendall was a prospective candidate for promotion to associate professor. According to a rumor at the time, Mehl's rejection of the Kirkendall Effect stopped Kirkendall from receiving the promotion to associate professorship, and he gave up to pursue his academic career and change his job to secretary of [AIME](#). Was it true?

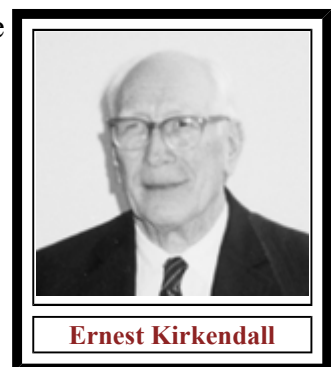

This question was my motivation to investigate the episode relating to Kirkendall. I was invited to his home and had already spent as long as six hours enjoyably talking with him. If I were to ask such a severe question directly, I was afraid that I would be impolite. But if I did not, I might regret it later without having solved the problem. Accidentally (and fortunately), he offered me his favorite Danish schnapps, [Cherry Heering](#). My feelings became more comfortable, and I realized this was a good opportunity to ask such severe questions. The doctor replied, "My promotion to associate professor had already been approved. The rumor was never reliable! The salary of the secretary of the [AIME](#) headquarters in New York City was attractive; it was more than twice the university's just after [World War II](#). I had three children and had to pay high tuitions for their schools and living expenses if living away from home. For this economic reason, I preferred the job change."

I asked him if he would have continued his research career if more people had accepted the Kirkendall Effect earlier, but he replied that he did not attribute much significance to the discovery, at least at that time. Although C.S. Smith tried to persuade him to stay at the university, he preferred the administrative job from an economic point of view, and even if he had accepted the promotion and stayed at the university, he would not have had any positive prospects for his research because of insufficient research facilities.

## CONCLUSION

After Kirkendall retired from his research life, he did not see Mehl for a long time. However, he visited Mehl just before he died. Mehl heartily apologized to Kirkendall for his strong opposition concerning his review of the third paper. He added, "I wish *I* had an effect which had my name like your Kirkendall Effect," and he asked Kirkendall to shake hands and be reconciled.

## ACKNOWLEDGEMENTS

*I appreciate Dr. and Mrs. Kirkendall for their invitation, fruitful conversation, and useful comments on the manuscript. I express my condolences to the loss of Mrs. Kirkendall on January 5, 1997. I also thank S. Rothman of [Argonne National Laboratory](#) and J. Manning of the [National Institute of Standards and Technology](#), M. Koiwa of [Kyoto University](#), J. Philibert of the University of Paris, and A.D. LeClaire of the [Open University](#) for useful information, and R.W. Cahn of the [University of Cambridge](#) for valuable comments on the manuscript.*

## References

1. W.C. Roberts-Austen, *Phil. Trans. Roy. Soc.*, A187 (1896), pp. 383-415.
2. E. Kirkendall, L. Thomassen, and C. Upthegrove, "Rates of Diffusion of Copper and Zinc in Alpha Brass," *Trans. AIME*, 133 (1939), pp. 186-203.
3. E.O. Kirkendall, "Diffusion of Zinc in Alpha Brass," *Trans. AIME*, 147 (1942), pp. 104-110.
4. A.D. Smigelskas and E.O. Kirkendall, "Zinc Diffusion in Alpha Brass," *Trans. AIME*, 171 (1947), pp. 130-142.
5. C.H. Desch, *Repts. Brit. Assn. for Advancement of Sci.*, 82 (1912), pp. 348-372.
6. R.F. Mehl, *Trans. AIME*, 122 (1936), pp. 11-56.
7. A.I. Krynetsky, *Metals and Alloys*, 8 (1937), pp. 138-144; 173-179; 261.
8. H.B. Huntington and F. Seitz, *Phys. Rev.*, 61 (1942), pp. 315-325.
9. *Atom Movements* (Metals Park, Ohio: [ASM](#), 1951).
10. L.C.C. daSilva and R.F. Mehl, *Trans. AIME*, 191 (1951), pp. 155-173.

---

### ABOUT THE AUTHOR

Hideo Nakajima is currently a professor at the [Institute of Scientific and Industrial Research at Osaka University](#).

---

Copyright held by [The Minerals, Metals & Materials Society](#), 1997

Direct questions about this or any other JOM page to [jom@tms.org](mailto:jom@tms.org).

<a href="#">Search</a>	<a href="#">TMS Document Center</a>	<a href="#">Subscriptions</a>	<a href="#">Other Hypertext Articles</a>	<a href="#">JOM</a>	<a href="#">TMS OnLine</a>
------------------------	-------------------------------------	-------------------------------	--	---------------------	----------------------------